

BRITISH STANDARD

**BS EN ISO
14632:1999**

Extruded sheets of polyethylene (PE-HD) — Requirements and test methods

The European Standard EN ISO 14632:1998 has the status of a
British Standard

ICS 83.080.20

NO COPYING WITHOUT BSI PERMISSION EXCEPT AS PERMITTED BY COPYRIGHT LAW



BS EN ISO 14632:1999

National foreword

This British Standard is the English language version of EN ISO 14632:1998. It is identical with ISO 14632:1998.

The UK participation in its preparation was entrusted to Technical Committee PRI/75, Plastics and rubber film and sheets, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

Attention is drawn to the fact that CEN and CENELEC Standards normally include an annex which lists normative references to international publications with their corresponding European publications. The British Standards which implement these international or European publications may be found in the BSI Standards Catalogue under the section entitled "International Standards Correspondence Index", or by using the "Find" facility of the BSI Standards Electronic Catalogue.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN ISO title page, pages 2 to 11 and a back cover.

Amendments issued since publication

Amd. No.	Date	Text affected

This British Standard, having been prepared under the direction of the Sector Committee for Materials and Chemicals, was published under the authority of the Standards Committee and comes into effect on 15 March 1999

© BSI 03-1999

ISBN 0 580 32254 8

EUROPEAN STANDARD

EN ISO 14632

NORME EUROPÉENNE

EUROPÄISCHE NORM

December 1998

ICS 83.140

Descriptors: plastics, polyethylene, extruded products, plates, designation, delivery condition, dimensions, dimensional tolerances, mechanical properties, thermal properties, tests, marking

English version

Extruded sheets of polyethylene (PE-HD) - Requirements and test methods (ISO 14632:1998)

Plaques extrudées en polyéthylène (PE-HD) - Prescriptions et méthodes d'essai (ISO 14632:1998)

Extrudierte Tafeln aus Polyethylen (PE-HD) - Anforderungen und Prüfverfahren (ISO 14632:1998)

This European Standard was approved by CEN on 2 October 1998.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Central Secretariat: rue de Stassart, 35 B-1050 Brussels

© 1998 CEN All rights of exploitation in any form and by any means reserved worldwide for CEN national Members.

Ref. No. EN ISO 14632:1998 E

Foreword

The text of EN ISO 14632:1998 has been prepared by Technical Committee CEN/TC 249 "Plastics", the secretariat of which is held by IBN, in collaboration with Technical Committee ISO/TC 61 "Plastics".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 1999, and conflicting national standards shall be withdrawn at the latest by June 1999.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Annex A is normative.

www.parsethylene-kish.com

1 Scope

This standard specifies the requirements and test methods for solid flat extruded sheets of polyethylene homopolymers (PE - HD) without fillers or reinforcing materials. This standard applies only to thicknesses of 0,5 mm to 40 mm. This standard also applies to PE - HD sheet in rolled form.

2 Normative references

This European standard incorporates, by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN ISO 179	Plastics - Determination of Charpy impact strength (ISO 179:1993)
EN ISO 291	Plastics - Standard atmospheres for conditioning and testing (ISO 291:1997)
EN ISO 527- 1	Plastics - Determination of tensile properties Part 1: General principles (ISO 527-1:1993 including Corr 1:1994)
EN ISO 527-2	Plastics - Determination of tensile properties Part 2: Test conditions for moulding and extrusion plastics (ISO 527-2:1993 including Corr 1:1994)
ISO 1 133	Plastics - Determination of the melt mass - flow rate (MFR) and the melt volume - flow rate (MVR) of thermoplastics
ISO 1 183	Plastics - Methods for determining the density and relative density of non - cellular plastics
ISO 1 872-1	Plastics - Polyethylene (PE) moulding and extrusion materials Part 1: Designation system and basis for specifications
EN ISO 2 818	Plastics - Preparation of test specimens by machining (ISO 2818:1994)
ISO/ TR 9 080	Thermoplastics pipes for the transport of fluids - Methods of extrapolation of hydrostatic stress rupture data to determine the long-term hydrostatic strength of thermoplastics pipe materials

3 Material

Sheets consist of PE extrusion compounds designated by ISO 1 872-1 without fillers or reinforcing materials. Extrusion compounds can contain additives such as processing aids, stabilisers, flame protective agents and colorants.

Compounds and additives of unknown identity shall not be used.

NOTE: Legal requirements can cause a specific choice of extrusion compounds (see 4.3.3).

4 Requirements

4.1 Appearance

Sheets shall be substantially free from bubbles, voids, cracks, visible impurities and other defects which would make them unfit for the intended use. Surfaces shall be substantially smooth and free from sharp grooves, sink marks or damage.

Colorants shall be homogeneously distributed throughout the material. Slight colour differences due to the particular extrusion compound or processing procedure used are admissible. Admissible variations in any of the above shall be agreed between the interested parties.

Sheets shall be examined in accordance with 5.3.

4.2 Dimensional tolerances

4.2.1 Thickness

Within any individual sheet, referring to the nominal thickness, the tolerance on thickness shall be:

$$|\Delta h| \leq \pm 10,08 \text{ mm} + 0,03 \times h_n \quad (1)$$

Where:

Δh is the tolerance on thickness, in millimetres
 h_n is the nominal thickness, in millimetres

Testing shall be in accordance with 5.4.1.

4.2.2 Length and width

Nominal length, l_n , and nominal width, b_n , of sheets shall be agreed between the interested parties. Unless agreed differently, the length shall be in the direction of extrusion.

For any individual sheet selected at random from any delivery, the tolerances on length and width shall be in accordance with table 1. Testing shall be in accordance with 5.4.2.

Table 1: Tolerances for length and width of sheet

Nominal value of dimension, D_n	Tolerances	
	Length	Width
$D_n \leq 500$	+ 2 - 1	+ 2 - 1
$500 < D_n \leq 1\,000$	+ 3 - 1	+ 3 - 1
$1\,000 < D_n \leq 1\,500$	+ 4 - 1	+ 4 - 1
$1\,500 < D_n \leq 2\,000$	+ 6 - 1	+ 4 - 1
$2\,000 < D_n \leq 3\,000$	+ 8 - 1	+ 6 - 1
$3\,000 < D_n \leq 4\,000$	+ 11 - 1	+ 7 - 1

For rolled sheets the minimum length shall be the nominal length.

4.2.3 Rectangularity

For any individual sheet, selected at random from any delivery, the rectangularity tolerance expressed as the difference between the length of the diagonals ($|d_1 - d_2|$, see figure 1) shall be in accordance with table A.1 of annex A (normative)

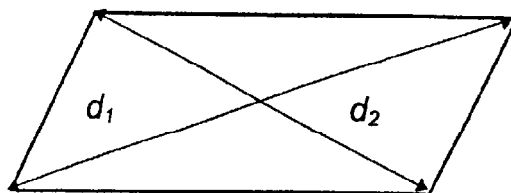


Figure 1: Difference between diagonals ($|d_1 - d_2|$)

Testing shall be in accordance with 5.4.3.

4.2.4 Bow of sheets in rolled form

For sheets in rolled form, a maximum bow of 20 mm in 10 metres length is permissible. Testing shall be in accordance with 5.4.4.

4.3 Properties

4.3.1 Mechanical and thermal properties

Table 2: Mechanical and thermal properties

Properties	Unit	Requirements (average values)				Test method subclause
		PE-HD sheet group				
		1 ¹⁾	2	3	4	
Density	g/cm ³	0,95 to 0,96	0,94 to 0,96	0,95 to 0,96	≥ 0,96	5.5
Tensile stress at yield	MPa	≥ 20	≥ 15	≥ 20	≥ 25	5.6
Tensile strain at yield	%	≥ 10	≥ 8	≥ 8	≥ 8	5.6
Modulus of elasticity in tension	MPa	≥ 700	≥ 700	≥ 900	≥ 1200	5.7
Charpy impact strength of notched specimens	kJ/ m ²	≥ 10	≥ 6	≥ 10	≥ 15	5.8
MFR 190 °C / 5 kg	g/ 10 min	0,4 to 0,7	0,1 to 2,0	0,1 to 2,0	0,1 to 2,0	5.9

¹⁾Sheets of group 1 shall be manufactured from extrusion compounds (black, UV-stabilized with >2 % carbon black) complying with specific requirements for creep rupture strength defined in accordance with ISO/ TR 9 080 and shall be approved by all interested parties.

4.3.2 Behaviour after heating

4.3.2.1 Maximum shrinkage for general applications

For general applications, the maximum shrinkage in the direction of extrusion shall be less than three percent after heating. Testing shall be in accordance with 5.10 and table 5.

4.3.2.2. Maximum shrinkage for thermoforming applications

The maximum shrinkage in the direction of extrusion shall not exceed the values given in table 3 when measured using the method in 5.10 and the conditions given in table 6.

Table 3: Maximum shrinkage for thermoforming applications

Nominal thickness, h_n (mm)	0,5	1	2	4	6	8	10	> 10
Maximum shrinkage in the direction of extrusion (%)	75	70	60	50	40	35	30	not applicable

4.3.3 Physiological behaviour

Relevant legislation concerning physiological behaviour shall be taken into consideration.

5 Test methods**5.1 Test specimens****5.1.1 Preparation of test specimens**

Representative test specimens shall be cut longitudinally and transversely from locations evenly distributed over the length and width of the sheet.

From a sheet in roll form, a two metre sample shall be cut from the end of the roll to provide test specimens.

Surfaces of the test specimens shall be free from damage and other defects in order to avoid notch effects. Should any burrs occur on the test specimens during production these shall be eliminated without damaging the surfaces of the test specimen. If required, the cut edges shall be finished with abrasive paper (grain number 220 or finer), the direction of abrasion being along the length of the test specimens. If it is necessary to machine the sheet to reduce it to the thickness required, one original surface shall be left intact. In particular, test specimens over 4,2 mm thick intended to be used in the tests described in 5.6 to 5.8 shall be machined down on one side to a thickness of 4,0 mm \pm 0,2 mm in accordance with EN ISO 2 818.

5.1.2 Conditioning

All test specimens shall be conditioned for at least 16 hours at standard atmosphere (23) in accordance with EN ISO 291. Shorter conditioning times shall be used by agreement between the interested parties when it can be shown that there is no significant difference in the results obtained.

5.1.3 Testing

Testing shall be carried out at standard atmosphere (23) in accordance with EN ISO 291, unless agreed differently between the interested parties or specified differently in the individual testing standards.

5.2 Delivery condition

Sheets should be visually examined when delivered to ensure freedom from mechanical damage or other obvious defects. Sheets can be inspected by means of ultrasonics or X-rays where required.

5.3 Appearance

Where possible, sheets shall be examined for visual defects by transmitted light using a suitable light source. Otherwise, sufficiently bright reflected light should be used. Any defects thus identified shall be compared with the agreed specification (either in written or sample form) and sentenced accordingly.

5.4 Dimensions

5.4.1 Thickness (h)

The thickness, h , shall be measured using a suitable calibrated equipment according to table 4:

Table 4: Accuracy of equipment

Dimensions in millimetres	
Nominal thickness, h_n	Accuracy
$0,50 \leq h_n \leq 1,00$	$\leq + 0,01$
$1,00 < h_n \leq 10,00$	$\leq + 0,05$
$10,00 < h_n \leq 40,00$	$\leq + 0,10$

5.4.2 Length (l) and width (b)

The length, l , and width, b , shall be measured to the nearest 1 mm using a suitable calibrated equipment. Measurements shall be made directly on the surface of the sheet and along the cut edge.

5.4.3 Rectangularity

For flat sheets, the rectangularity expressed as the difference between the length of the diagonals according to figure 1, $|d_1 - d_2|$, shall be measured to the nearest 1 mm using a calibrated ruler or tape measure.

5.4.4 Bow of sheets in rolled form

For sheets in rolled form, the bow shall be determined after the sheets have been pulled freely from the rolls and measured against a straight line. The bow shall be measured to the nearest 1 mm using a suitable calibrated equipment.

5.5 Density

Density shall be determined in accordance with ISO 1 183.

5.6 Tensile stress at yield (σ_y) and tensile strain at yield (ε_y)

Tensile stress at yield, σ_y , and tensile strain at yield, ε_y , shall be determined using at least five type 1B test specimens in each direction in accordance with EN ISO 527- 1 and EN ISO 527- 2 using a test speed of 50 mm/min \pm 5 mm/min.

5.7 Modulus of elasticity in tension (E)

Modulus of elasticity in tension, E_t , shall be determined using at least five type 1B test specimens in each direction in accordance with EN ISO 527- 1 and EN ISO 527-2 using a test speed of 1 mm/min \pm 0,2 mm/min.

5.8 Charpy impact strength of notched specimens (a_{cn})

Charpy impact strength of notched specimens, a_{cn} , for nominal thicknesses ≥ 4 mm shall be determined in accordance with EN ISO 179/ 1eA using at least 10 test specimens in each direction.

5.9 Melt mass-flow rate (MFR)

Melt mass-flow rate (MFR 190/ 5) shall be determined in accordance with ISO 1 133.

5.10 Determination of shrinkage after heating

At least three test specimens with dimensions of 100 mm x 100 mm shall be cut from the centre and two sides of the sheet. The side test specimens shall be taken at least 50 mm from the edge of the sheet. The extrusion direction of the sheet shall be marked on the specimens at a minimum of two places. The initial length, L_0 , in the direction of extrusion shall be measured on the marked places with an accuracy of 0,1 mm after conditioning of the specimens in accordance with EN ISO 291. The specimens shall be dusted with kaolin and shall be placed flat on a kaolin bed in an oven with air circulation. The temperature and duration of the test are shown in table 5 and table 6.

Table 5: Shrinkage for general applications

Nominal thickness, h_n mm	Test temperature °C	Duration of test ¹⁾ min
$0,5 \leq h_n \leq 2$	110 ± 2	60 ± 1
$2 < h_n \leq 10$	110 ± 2	90 ± 1
$10 < h_n \leq 20$	110 ± 2	120 ± 1
$20 < h_n \leq 40$	110 ± 2	240 ± 1

¹⁾The heating period until the test temperature is reached is not included.

Table 6: Shrinkage for thermoforming applications

Nominal thickness h_n mm	Test temperature °C	Duration of test ¹⁾ min
$0,5 \leq h_n \leq 1$	170 ± 2	10 ± 1
$1 < h_n \leq 2$	170 ± 2	35 ± 1
$2 < h_n \leq 10$	170 ± 2	60 ± 1

¹⁾The heating period until the test temperature is reached is not included.

After removal of the test specimen from the oven and conditioning in accordance with EN ISO 291, the length shall be measured at the marked places. The shrinkage, ΔL , shall be calculated on each marked place using equation (2):

$$\Delta L = \frac{L - L_0}{L_0} \times 100 \tag{2}$$

Where: ΔL is the shrinkage after heating, in percent
 L_0 is the initial length in the direction of extrusion before heating, in millimetres
 L is the length in the direction of extrusion after heating, in millimetres

The arithmetic mean shall be calculated of all the values of ΔL for all specimens.

6 Designation

6.1 Example for PE- HD sheets

5 sheets EN ISO 14 632 PE-HD-1 - 8 x 2 000 x 1 000 - black

Number of items	5
Form in which supplied	sheets
Number of standard	EN ISO 14 632
Group	PE-HD-1
Nominal thickness in millimetres	8
Nominal length in millimetres	2 000
Nominal width in millimetres	1 000
Colour	black

6.2 Example for PE- HD sheets in rolled form

500 rolled sheet EN ISO 14 632 PE-HD-1 - 1 x 1 000 x 76 x 1 000 - black

Quantity in kilogrammes	500
Form in which supplied	rolled sheet
Number of standard	EN ISO 14 632
Group	PE-HD-1
Nominal thickness in millimetres	1
Maximum diameter of roll in millimetres	1 000
Inner diameter of core piece in millimetres	76
Nominal width of roll in millimetres	1 000
Colour	black

7 Marking

Sheets that conform to this standard are allowed to be marked with the following information:

- the manufacturer's name, trade mark or identification mark
- the number of this Standard, EN ISO 14 632
- date of manufacture / batch number

www.parsethylene-kish.com

ANNEX A (normative)

Requirements for rectangularity

Table A.1: Rectangularity tolerances (see 4.2.3)

Dimensions in millimetres	
Nominal sheet dimension	Maximum value for the rectangularity tolerance
Length x Width	$ d_1 - d_2 $
≤ 550 x 1 000	3
> 550 to 900 x 1 000	4
> 900 to 1 500 x 1 000	5
> 1 500 to 4 000 x 1 000	6
≤ 550 x 1 220	3
> 550 to 800 x 1 220	4
> 800 to 1 100 x 1 220	5
> 1 100 to 1 750 x 1 220	6
> 1 750 to 4 000 x 1 220	7
≤ 550 x 1 500	3
> 550 to 750 x 1 500	4
> 750 to 1 000 x 1 500	5
> 1 000 to 1 350 x 1 500	6
> 1 350 to 1 850 x 1 500	7
> 1 850 to 3 000 x 1 500	8
> 3 000 to 4 000 x 1 500	9
≤ 500 x 2 000	3
> 500 to 700 x 2 000	4
> 700 to 900 x 2 000	5
> to 1 150 x 2 000	6
> 1 150 to 1 450 x 2 000	7
> 1 450 to 1 800 x 2 000	8
> 1 800 to 2 300 x 2 000	9
> 2 300 to 3 000 x 2 000	10
> 3 000 to 4 000 x 2 000	11
≤ 500 x 3 000	3
> 500 to 700 x 3 000	4
> 700 to 850 x 3 000	5
> 850 to 1 050 x 3 000	6
> 1 050 to 1 250 x 3 000	7
> 1 250 to 1 500 x 3 000	8
> 1 500 to 1 700 x 3 000	9
> 1 700 to 2 000 x 3 000	10
> 2 000 to 2 300 x 3 000	11
> 2 300 to 2 700 x 3 000	12
> 2 700 to 3 100 x 3 000	13
> 3 100 to 3 700 x 3 000	14
> 3 700 to 4 000 x 3 000	15

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 0181 996 9000. Fax: 0181 996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 0181 996 7000. Fax: 0181 996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 0181 996 7111. Fax: 0181 996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 0181 996 7002. Fax: 0181 996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 0181 996 7070.